

Temperature-dependent density of states in the organic superconductor κ -(BEDT-TTF) $_2$ Cu[N(CN) $_2$]Br

Sandra Diehl,^{1,2,*} Torsten Methfessel,² Jens Müller,³ Michael
Lang,³ Michael Huth,³ Martin Jourdan,² and Hans-Joachim Elmers²

¹Graduate School Materials Science in Mainz, Staudingerweg 9, 55128 Mainz, Germany

²Institut für Physik, Johannes Gutenberg-Universität Mainz, Staudingerweg 7, 55128 Mainz, Germany

³Physikalisches Institut, Goethe-Universität Mainz,

Max-von-Laue-Str. 1, 60438 Frankfurt am Main, Germany

(Dated: October 20, 2014)

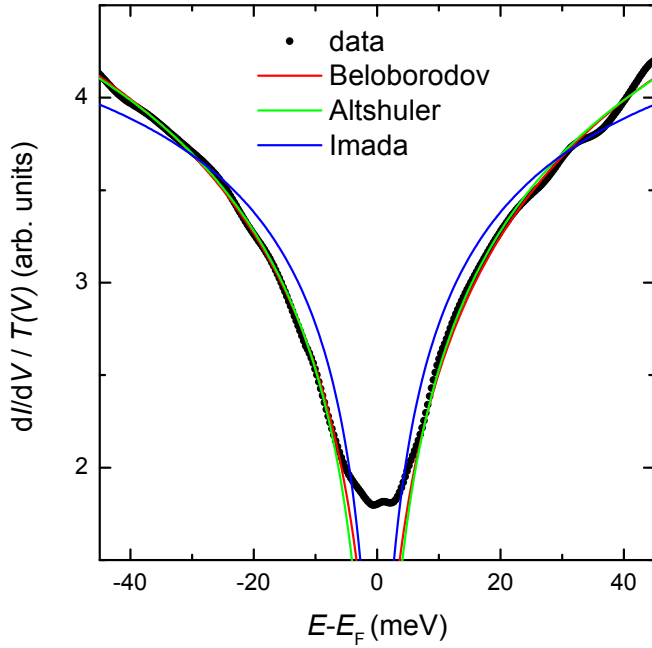


FIG. 1. Comparison of the models proposed by Beloborodov, Altshuler and Imada et al. The model of Imada et al. (blue line) does not fit to the measured data. Whereas the model of Altshuler (green line) and Beloborodov (red line) describe the data qualitatively well. A quantitative description with reasonable fitting parameters is only possible with the model of Beloborodov et al. The fitting parameters obtained from the fit with Altshulers model deviate in orders of magnitude from values obtained by rough calculations.

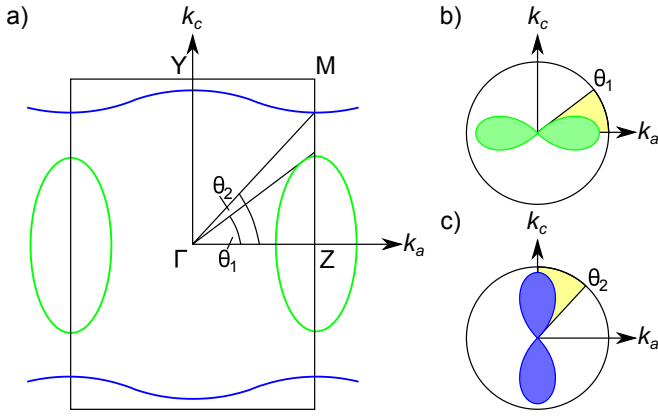


FIG. 2. a) Due to the twofold Fermi surface of the κ -Br crystals there are two different contributions to the measured superconducting gap function leading to two different values of the gap width Δ . b),c) Therefore, it is necessary to use $\frac{c_1}{\theta_1} \int_0^{\theta_1} d\theta \frac{E+i\Gamma}{\sqrt{(E+i\Gamma)^2 - (\Delta_1(\theta))^2}} + \frac{c_2}{\pi/2-\theta_2} \int_{\theta_2}^{\pi/2} d\theta \frac{E+i\Gamma}{\sqrt{(E+i\Gamma)^2 - (\Delta_2(\theta))^2}}$ for the determination of the two different values of the gap width.

TABLE I. Comparison of the different models.

Beloborodov	$\gamma \left(1 - \frac{1}{4\pi g_T^0} \ln \left(\frac{g_T^0 E_C}{ eV } \right) \right)^{4g_T^0}$
Althuler	$\beta \left(1 - \frac{\hbar}{2\pi E_F \tau} \ln \left(E \frac{\tau}{\hbar} \right) \ln \left(\left \frac{E}{\hbar D \kappa^2} \right \right) \right)$
Imada	$\alpha \exp(-\sqrt{(\epsilon_0/\epsilon)})$

TABLE II. Fit parameters of fit with the Dynes function.

T (K)	Δ_1 (meV)	Δ_2 (meV)	Γ (meV)
5	2.80	6.4	1.80
7	2.40	5.4	1.45
9	2.05	4.8	1.35
11	1.35	3.2	0.80